

Incorporation of Oxygen in Crystalline Zeolitic Chromosilicates: Optical Identification of Chromium(VI) by Photoacoustic Spectroscopy

J. Silvio T. Mambrim,^a Eduardo J. S. Vichi,*^a Heloise O. Pastore,^a Celso U. Davanzo,^a Helion Vargas,^b Edson Silva^b and Ossamu Nakamura^c

^a Instituto de Química, Universidade Estadual de Campinas, C. Postal 6154, 13081 Campinas, SP, Brazil

^b Instituto de Física, Universidade Estadual de Campinas, 13081 Campinas, SP, Brazil

^c Instituto de Física, Universidade Federal da Bahia, Salvador, BA, Brazil

Incorporation of oxygen to crystalline zeolitic chromosilicates, with oxidation of anchored Cr^{III} to non-interacting Cr^{VI} species, has been confirmed by photoacoustic spectroscopy; the dichromate anion being extracted from the chromosilicate with water and identified by precipitation of AgCrO₄ and oxidation to CrO₅.

The study of the state of chromium ions in high-content silica zeolites is of great interest since new polyfunctional catalysts can be designed with these systems.¹ It was recently shown that both Cr^{III} and Cr^V ions can be incorporated in the cationic positions of zeolites of the ZSM-5 type.²

In a recent communication³ we reported on the preparation of a highly crystalline zeolitic chromosilicate containing Cr^{III}

both in framework, and non-framework positions, the latter probably anchored inside the channels and forming species similar to Cr₂O₃. Here we report on the obtention of Cr^{VI} species during the process of calcination of this chromosilicate.

After heating a sample of this chromosilicate at 693 K for 24 h, in a shallow bed, under an oxygen flow, its colour

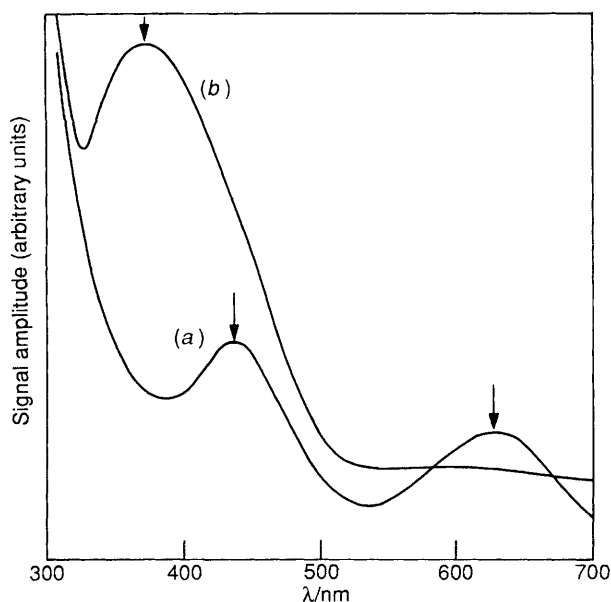


Fig. 1 PAS spectra of chromium in crystalline zeolitic chromosilicates, (a) ligand field bands of Cr^{III}, (b) charge transfer band of Cr^{VI}

changed from light green to yellow. The presence of Cr^{VI}, was detected by means of photoacoustic spectroscopy (PAS), which is rapidly achieving importance as a technique for obtaining ultraviolet, visible and near-infrared absorption of opaque or highly scattering samples such as powders, glasses, gels and turbid liquids.⁴ The recorded spectrum is identical to that from conventional spectroscopic techniques.⁵

The spectrum of a freshly prepared sample of the chromosilicate is shown in Fig. 1(a), and is characterized by two bands centred at 440 and 640 nm, respectively, corresponding to ligand field bands of Cr^{III}. For the level assignment⁶ the band centred at 440 nm is interpreted as the ${}^4\Gamma_2 \rightarrow {}^4\Gamma_4$ (F) transition, and the band at 640 nm is interpreted as the ${}^4\Gamma_2 \rightarrow {}^4\Gamma_5$ transition. Fig. 1(b) shows the spectrum of the same sample after being treated with oxygen as previously described. A strong band at 370 nm is clearly seen, which is assigned to a charge transfer absorption of Cr^{VI}. The second charge transfer occurring at 270 nm was not observed since our equipment (an EDT-model OAS spectrometer) is limited to the range of 300 to 700 nm.

Fig. 2 shows the IR spectra of (a) the original sample, (b) the sample treated with oxygen at 693 K, and (c) the sample treated with dioxygen at 843 K. The sample calcined at 693 K retained its zeolitic crystal structure as shown by the 550:440 cm⁻¹ optical density ratios equal to 0.77, for (a), and 0.74 for (b). However, heating the sample at 843 K leads to the collapse of the crystal structure of the pentasil zeolites, as shown by the disappearance of the peaks at 550 and 450 cm⁻¹ [Fig. 2(c)].

The yellow colour of the calcined chromosilicate strongly suggests that Cr^{VI} is bonded to extraframework O²⁻ ligands forming anionic species like CrO₄²⁻ or Cr₂O₇²⁻. It is probable that the anchored and activated Cr₂O₃ species incorporate oxygen to form CrO₃ which is then hydrolysed during the rehydration of the zeolite. In fact, washing the sample with cold water leads to the easy and almost quantitative extraction of the chromates. The chromates were identified in the extracts by the precipitation of the reddish-brown Ag₂CrO₄



Fig. 2 IR spectra of (a) the original chromosilicate sample, (b) the sample treated with oxygen at 693 K, (c) the sample treated with oxygen at 843 K

after addition of an aqueous solution of AgNO₃, and by the formation of blue CrO₅, in diethyl ether, after addition of 3% hydrogen peroxide and dilute HNO₃.⁷

The retention of the zeolitic crystal structure upon heating to 693 K suggests that, at this temperature, only the extra-framework Cr^{III} ions react with oxygen producing chromates. It is impossible to say, at this stage, if the breakdown of the zeolitic framework, at 843 K, is caused by thermal expulsion of Cr^{III} from the silicon lattice or by thermal activation towards oxygen attack.

We are investigating the dehydration/rehydration processes and the reversibility of the oxidation process in an attempt to explore all the potentialities of this very interesting system.

We gratefully acknowledge FAPESP and CNPq for financial support.

Received, 13th February 1991; Com. 1/00685A

References

- 1 R. B. Borade, A. B. Halgeri, and T. S. R. P. Rao, *Advances in Catalysis Science and Technology*, Wiley Eastern, New Delhi, 1985, p. 389.
- 2 A. V. Kucherov and A. A. Slinkin, *Zeolites*, 1987, **28**, 81; A. V. Kucherov and A. A. Slinkin, *Kinet. Katal.*, 1986, **27**, 1199.
- 3 H. O. Pastore, E. Stein, C. U. Davanzo, E. J. S. Vichi, O. Kakamura, M. Baesso, E. Silva and H. Vargas, *J. Chem. Soc., Chem. Commun.*, 1990, 772.
- 4 H. Vargas and L. C. M. Miranda, *J. Phys. Rep.*, 1988, 161; 245.
- 5 A. Rosencwaig, *Photoacoustics and Photoacoustic Spectroscopy*, Wiley, New York, 1980.
- 6 Y. Tanabe and S. Sugano, *J. Phys. Soc. Jpn.*, 1954, **9**, 753; 766.
- 7 I. Vogel, *Textbook of Macro and Semimicro Qualitative Inorganic Analysis*, Longman, London, 5th edn., 1979, p. 361 and 362.